

## REPORT DOCUMENTATION PAGE

DTIC

AD-A231 675

1b. RESTRICTIVE MARKINGS

2b. DECLASSIFICATION/DOWNGRADING SCHEDULE

3. DISTRIBUTION/AVAILABILITY OF REPORT

Approved for public release  
distribution unlimited

4. PERFORMING ORGANIZATION REPORT NUMBER(S)

Technical Report # 58

5. MONITORING ORGANIZATION REPORT NUMBER(S)

6a. NAME OF PERFORMING ORGANIZATION  
Dept. of Chemistry  
George Washington Univ.6b. OFFICE SYMBOL  
(if applicable)

7a. NAME OF MONITORING ORGANIZATION

Office of Naval Research (Code 418)

6c. ADDRESS (City, State, and ZIP Code)

Washington, DC 20052

7b. ADDRESS (City, State, and ZIP Code)

Chemistry Program  
800 N. Quincy Street  
Arlington, VA 222178a. NAME OF FUNDING/SPONSORING  
ORGANIZATION

Office of Naval Research

8b. OFFICE SYMBOL  
(if applicable)

9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER

Contract N00014-89-J-1103

8c. ADDRESS (City, State, and ZIP Code)

Chemistry Program  
800 Nth, Quincy, Arlington, VA 22217

10. SOURCE OF FUNDING NUMBERS

PROGRAM  
ELEMENT NO.PROJECT  
NO.TASK  
NO.R & T  
4134043-01WORK UNIT  
ACCESSION NO.

11. TITLE (Include Security Classification)

CEELS as a Probe of the Carbide to Graphite Transformation on Ni  
(Unclassified)

12. PERSONAL AUTHOR(S)

David E. Ramaker

13a. TYPE OF REPORT

Interim Technical

13b. TIME COVERED

FROM TO

14. DATE OF REPORT (Year, Month, Day)

January 1991

15. PAGE COUNT

10

16. SUPPLEMENTARY NOTATION

Prepared for publication in Proc. 2nd Intl. Conf. New Diamond Sci. & Tech.  
(Materials Res. Soc.)

17. COSATI CODES

FIELD GROUP SUB-GROUP

18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)

Carbide Nucleation Electron Energy Loss

Graphite X-ray Absorption

19. ABSTRACT (Continue on reverse if necessary and identify by block number)

Recent effective medium theory calculations indicate that a nucleation step must be involved in the carbide to graphite transformation on Ni, and that vertical C<sub>2</sub> may be a precursor to this nucleation step. A similar nucleation site could also be involved in diamond formation on metals. We interpret previously published C K edge CEELS and NEXAFS data for carbon/Ni between 500-700K. We make comparison with theoretical DOS calculations, and utilize CEELS angle dependencies to assign features and determine bond orientations on the surface. The results confirm that horizontal C<sub>n</sub>, most likely C<sub>2</sub>, exists on the surface up 600K, but that at 620K, some of the C<sub>2</sub> species flip up. Evidence for vertical C<sub>2</sub> is seen only at higher C coverages suggesting that indeed these vertical C<sub>2</sub>'s serve as the precursor for the nucleation of graphite, and perhaps also for diamond.

91 2 04 095

20. DISTRIBUTION/AVAILABILITY OF ABSTRACT

☒ UNCLASSIFIED/UNLIMITED☒ SAME AS RPT.☐ DTIC USERS

21. ABSTRACT SECURITY CLASSIFICATION

Unclassified

22a. NAME OF RESPONSIBLE INDIVIDUAL

Dr. Mark Ross

22b. TELEPHONE (Include Area Code)

(202) 696-4409

22c. OFFICE SYMBOL

OFFICE OF NAVAL RESEARCH

Contract N00014-89-J-1103

R & T Code 4134043-01

Technical Report No. 58

|                    |                                     |
|--------------------|-------------------------------------|
| Accession For      |                                     |
| NTIS GRA&I         | <input checked="" type="checkbox"/> |
| DTIC TAB           | <input type="checkbox"/>            |
| Unannounced        | <input type="checkbox"/>            |
| Justification      |                                     |
| By _____           |                                     |
| Distribution/      |                                     |
| Availability Codes |                                     |
| Dist               | Avail and/or<br>Special             |
| A-1                | 20                                  |

CEELS as a Probe of the Carbide to Graphite Transformation on NI

By

DAVID E. RAMAKER

Prepared for Publication

in

Proc. 2nd. Intn. Conf. New Diamond Sci. & Tech. (Mat. Res. Soc.)

George Washington University  
Department of Chemistry  
Washington, D.C.

January, 1991

Reproduction in whole or in part is permitted for  
any purpose of the United States Government

\* This document has been approved for public release  
and sale; its distribution is unlimited.

# CEELS AS A PROBE OF THE CARBIDE TO GRAPHITE TRANSFORMATION ON Ni

David E. Ramaker \*

Chemistry Division, Naval Research Laboratory, Washington, DC. 20375, USA

## ABSTRACT

Recent effective medium theory calculations indicate that a nucleation step must be involved in the carbide to graphite transformation on Ni, and that vertical  $C_2$  may be a precursor to this nucleation step. A similar nucleation site could also be involved in diamond formation on metals. We interpret previously published C K edge CEELS and NEXAFS data for carbon/Ni between 500-700K. We make comparison with theoretical DOS calculations, and utilize CEELS angle dependencies to assign features and determine bond orientations on the surface. The results confirm that horizontal  $C_n$ , most likely  $C_2$ , exists on the surface up to 600K, but that at 620K, some of the  $C_2$  species flip up. Evidence for vertical  $C_2$  is seen only at higher C coverages suggesting that indeed these vertical  $C_2$ 's serve as the precursor for the nucleation of graphite, and perhaps also for diamond.

## THE CARBIDE TO GRAPHITE TRANSFORMATION

Carbon is relatively unreactive with Ni. Thus Ni forms a relatively unstable carbide, which above 670K either undergoes dissolution into the bulk or at higher coverages forms a graphitic layer which sits high above the surface (e.g. 2.8 Å above a Ni(111) surface) [1]. Recent calculations utilizing effective medium theory (EMT) [1] shed some light on this transformation. In the EMT approach, the atom positions are determined by the electron density, each atom seeking its own unique optimum density. These calculations conclude that at intermediate coverage, the C-C interaction drives carbon closer to a Ni surface, but in a graphite layer, the C-C interaction drives carbon away from the surface. They conclude that the carbide to graphite evolution is discontinuous, indicating that a nucleation step must be involved.

The calculations also suggest that horizontal  $C_2$  species on a Ni(111) surface are not stable at high temperature, but that vertical (i.e. perpendicular)  $C_2$  species may be stable on the Ni surface [1]. However, this vertical  $C_2$  is too close to the surface to serve as a nucleation site for graphite formation by itself. A  $C_3$  species is the smallest entity which moves sufficiently far from the Ni surface to serve as a graphite nucleation site. Darling et al. [1] then postulate that a vertical  $C_2$  species may either "tip over" to form a  $C_3$  species, which moves

away from the surface to act as a graphite nucleation site, or a graphitic layer forms on top of a carbidic layer (i.e. the outer C of the vertical C<sub>2</sub> may become part of the graphite layer, and the inner C may ultimately undergo dissolution into the bulk). In either case, a vertical C<sub>2</sub> serves as a precursor to the nucleation site.

An identical nucleation step could be involved in the nucleation of diamond on metal surfaces, and critically determine the bonding of the diamond film to the metal. Thus we search for experimental confirmation of these theoretical results for graphite. NEXAFS (near edge x-ray absorption fine structure) data have been very helpful in determining the various orientations of molecular hydrocarbon fragments on Ni below 450 K [2], but little new information from NEXAFS data has been obtained for C/Ni above 450 K. In this work we utilize previously published [3,4] CEELS (core electron energy loss spectroscopy) and NEXAFS data [5] to obtain experimental verification that vertical C<sub>2</sub> acts as a precursor for graphite nucleation on Ni.

Recently Caputi et al. [3] reported AES and CEELS data for carbon on Ni(100) in the range 520-770 K. Core-level and valence band XPS data have also been reported [3]. A detailed interpretation of the AES and XPS data has revealed extensive C-C bonding on the surface, in what was previously believed to be carbidic (i.e. only C-M bonding) in character [6]. At higher temperatures, just prior to the formation of graphite around 620K, the AES data indicate that the amount of C-C bonding appears to decrease. No meaningful interpretation of the CEELS data in this same temperature range has been reported.

## CEELS ANGULAR DEPENDENCE

In NEXAFS, the dipole selection rule (i.e.  $s \rightarrow p$  only) is appropriate. By CEELS, we mean the use of small electron energies (500-1000 eV) and the measurement of back scattered electrons which have suffered large momentum transfer, in which case the validity of the dipole selection rule is not expected. Thus optically forbidden monopole transitions should be evident. Nevertheless, CEELS data can still be utilized to obtain some of the same information obtainable from NEXAFS data.

We utilize equations derived by Cheung [7] for determining the angular dependence of CEELS data for graphite, which has the  $\sigma$  orbital parallel to the surface. Cheung obtains,

$$\{1s \rightarrow \pi\} \propto 1.5\xi \sin^2 \delta + 3\nu [\cos^2 \delta - 0.5 \sin^2 \delta] \sin^2 \theta \quad (1)$$

$$\{1s \rightarrow \sigma\} \propto \xi/3 + \nu [1 - 0.5 \sin^2 \delta] - \nu [\cos^2 \delta - 0.5 \sin^2 \delta] \sin^2 \theta, \quad (2)$$

where  $\delta$  is the electron acceptance angle and  $\xi$  and  $\nu$  are the magnitude of the monopole and dipole contributions, respectively. Here  $\theta$  is the angle between

the surface and the electron beam direction. We compare these expressions with those appropriate for NEXAFS and C=C bonds parallel to the surface [2],

$$\{1s \rightarrow \pi\} \propto 6\cos^2\theta \quad (3)$$

$$\{1s \rightarrow \sigma\} \propto 3\sin^2\theta. \quad (4)$$

If we assume that  $\delta = 90^\circ$  in eqs. 1 and 2 (i.e. that electrons are counted at all acceptance angles), the CEELS technique mimics the NEXAFS technique, which utilizes the total electron yield or the Auger yield. We then obtain,

$$\{1s \rightarrow \pi\} \propto 1.5\nu \cos^2\theta \quad (5)$$

$$\{1s \rightarrow \sigma\} \propto \xi/3 + 0.5\nu + 0.5\nu \sin^2\theta. \quad (6)$$

These expressions have similar  $\sin^2\theta$  and  $\cos^2\theta$  dependences to those above for NEXAFS as expected. In contrast, if we assume  $\delta = 16.5^\circ$  (i.e. the appropriate acceptance angle for a cylindrical mirror analyzer and a 500 eV excitation beam as utilized by Cheung [7]), we obtain the expressions,

$$\{1s \rightarrow \pi\} \propto 0.12\nu + 2.64\nu \sin^2\theta \quad (7)$$

$$\{1s \rightarrow \sigma\} \propto \xi/3 + 0.08\nu + 0.88\nu \cos^2\theta. \quad (8)$$

Notice the switch in  $\cos^2\theta/\sin^2\theta$  dependence between eqs. 5, 6 and 7, 8. Eqs. 7 and 8, appropriate for this case, are also different from that for NEXAFS, eqs. 3 and 4. Furthermore, Cheung [7] found empirically for graphite with a 500 eV excitation beam that  $\xi/\nu$  is about 8. Thus in CEELS for  $\theta = 90^\circ$  (i.e. electron beam perpendicular to surface, which is generally the case for the data discussed in this work) the  $\pi$  and  $\sigma$  contributions have nearly equal intensity (eqs. 7 and 8 above both give  $2.75\nu$ ). If the C-C bond is vertical to the surface, we expect a corresponding reversal in the dipole intensity dependencies giving  $\{1s \rightarrow \pi\} = 0.08\nu$  and  $\{1s \rightarrow \sigma\} = 5.42\nu$ .

In summary, the CEELS data should give about equal  $\sigma$  and  $\pi$  area intensities for parallel C-C orientation, and be dominated by  $\sigma$  intensity for perpendicular C-C orientation.

## INTERPRETATION OF CEELS FEATURES

Figs. 1b and c compare  $-d^2N(E)/dE^2$  K edge CEELS curves for various carbonaceous layers on metals [3,4] along with NEXAFS data for CO/Ni(100) at 670K in 1d [5]. We have also included in Fig. 1a NEXAFS [8] data for condensed benzene and cyclohexane for comparison. NEXAFS data for a large number of molecules and solids show C-H and C-C  $\pi^*$  and  $\sigma^*$  features at surprisingly specific energies [8]; so we have labelled these features accordingly in Fig. 1a.

All of the carbonaceous layers were prepared by exposure of the Ni surfaces to CO at around 500K, and then heating. The dashed curve in 1b was


Fig. 1

a) C K NEXAFS data for condensed benzene and cyclohexane [5],

b)  $-d^2N(E)/dE^2$  C K edge CEELS data for CO/Ni(100) at 500K (dotted line) [3] and CO/Ni(111) at 520K (solid line) [4],

c) CEELS data for CO/Ni(100) at 620K [3], and

d) NEXAFS data for CO/Ni(100) at 670K, but at low coverage [5].

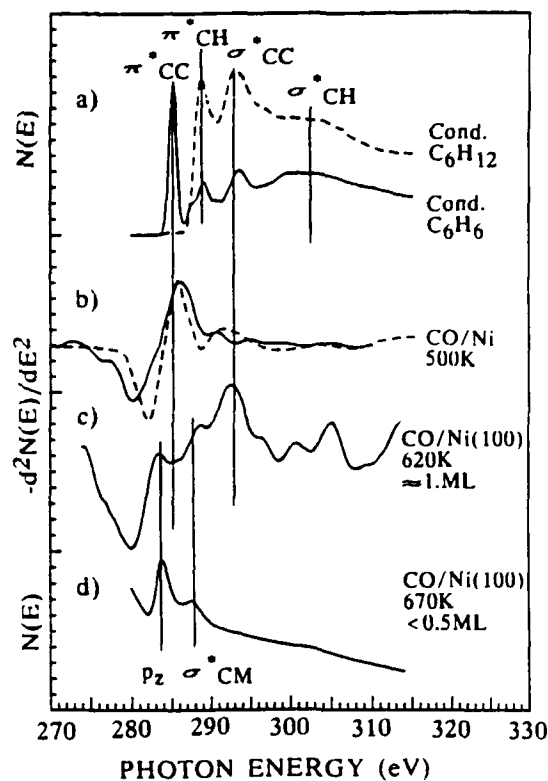

reported by Rosei et al [4] for a Ni(111) surface upon heating to 500K with an estimated coverage of about 0.3 ML (this is a very crude estimate). The solid curves in b (at 520K) and c (at 620K) were reported by Caputi et al [3]. Although they do not estimate the C coverage, it is believed to be greater than or equal to 1 ML. The NEXAFS curve in (d) was reported by Stohr and Jaeger [5] with incident angle  $\Theta = 20^\circ$ . Consistent with the expected NEXAFS angular dependence, this curve emphasizes vertical  $\sigma$  bonds. The latter curve corresponds to less than 0.5 ML of "carbide" C on the surface. The K binding energy is about 282.9 eV for a carbide layer on Ni(100) [9]. We have deconvoluted the Caputi data by a 2 eV Gaussian line shape to regain better resolution since it was taken with a large 6 V<sub>ptp</sub> modulation voltage.

The deconvoluted Caputi data on Ni(100) and the Rosei data on Ni(111) at 500 K are quite similar as expected. They reveal the characteristic  $\pi^*_{CC}$  and  $\sigma^*_{CC}$  peaks at 285 eV and 293 eV respectively as seen in the molecular NEXAFS data. Since C-M bonds do not produce peaks in this energy range [10], this clearly indicates the presence of C-C bonding on the surface, consistent with the AES and XPS data [6] as indicated above. The similar area intensities of the  $\pi^*_{CC}$  and  $\sigma^*_{CC}$  peaks indicate that the C-C bonds lie flat on the surface. We would assume that these C-C bonds primarily exist as  $C_n$  ( $n = 2, 3$  etc, with  $n=2$  favored) species on the surface.

The Caputi data at 620K (curve c) reveal dramatic differences from that at 520K. Now the  $\sigma^*_{CC}$  feature dominates with the  $\pi^*_{CC}$  feature nearly missing. This is consistent with C-C bonds perpendicular to the surface. We believe the  $\sigma^*_{CC}$  feature now arises from  $C_2$  species standing erect on the surface.

NEXAFS data for CO/Ni(100) at 300 K [5] (not shown) are dominated by the  $\pi^*$  and  $\sigma^*$  CO bond features. Heating to 670K breaks all C-O bonds, leaving only atomic C on the surface. Notice that in Fig. 2d, no evidence exist for either C-O or C-C bonds. The features at 284 and 288 eV are attributed [10] to nonbonding  $p_z$  orbitals and  $\sigma^*$  CM orbitals bonding the atomic C to the surface. Evidence for these same features also exists in the deconvolved 620K data of Caputi (curve 1c).

## COMPARISON WITH THEORETICAL DOS

Fig. 2 provides further evidence for our assignment of the  $p_z$  and  $\sigma^*$  CM features above. We compare NEXAFS data for NbC [11] and C/Ni (i.e. the data in Fig. 1) to DOS results for NbC reported by Schwarz [12] and for C/Ru reported by Feibelman [13]. Schwarz utilized a self-consistent augmented plane wave (APW)  $X_\alpha$  calculation for a periodic NbC solid. Feibelman's results were obtained for a (1x1) overlayer of C atoms on an 11-layer Ru(0001) film, with only 1/3 of the three-fold sites filled with carbon atoms. In this theoretical model, the carbon atoms are relatively isolated since the nearest C-C distance is greater than 5.0 a.u. compared with a C-C distance of 2.68 a.u. in graphite [13]. We believe Feibelman's results should be adequate for low coverages of C/Ni since both Ru and Ni form relatively unstable carbides compared with Nb or Ti.


The DOS from both calculations are available for only the first 10 eV or less of the conduction band.. Schwarz identified the two peaks in the DOS as the  $\pi^*$  and  $\sigma^*$  antibonding features (i.e. involving the  $t_{2g}$  and  $e_g$  Nb d orbitals). Feibelman identified the two major peaks for C/Ni as the  $p_z$  and  $\sigma^*$  features.

Fig. 2

Comparison of C K NEXAFS data for NbC and C/Ni with DOS calculations.

a) NEXAFS data from Wesner et al [11], shifted up in energy by 3.0 eV based on calibration with similar data for graphite. DOS calculation from Schwarz [12].

b) NEXAFS data from Stohr and Jaeger [5] for CO/Ni at 670K with DOS from Feibelman for a (1x1) layer of C on a Ru(0001) film.

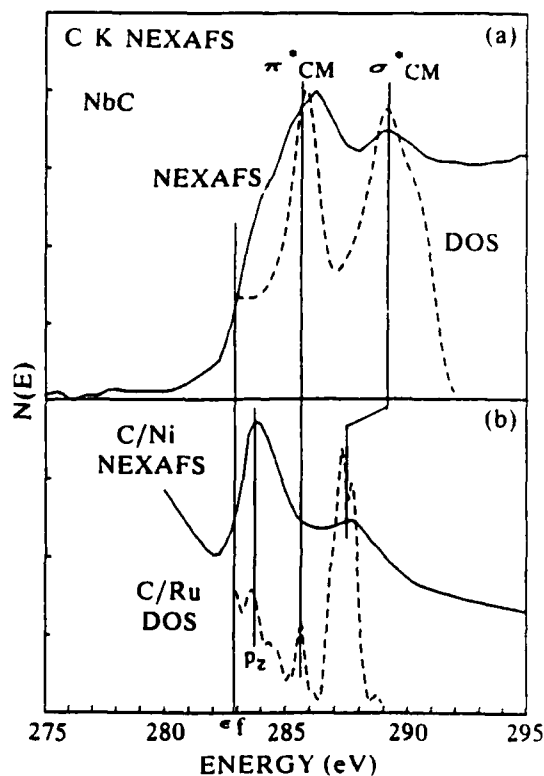

The  $p_z$  feature arises from the C nonbonding or "dangling" bonds pointing outward from the surface. The  $\sigma^*$  feature arises from the three  $sp^3$ -like C-metal bonds per C atom. Note that a similar  $\pi^*$  feature also appears in Feibelman's DOS and aligns with the same peak for NbC, but it has much weaker intensity. Furthermore, note that the  $\sigma^*$  feature has a much lower energy for C/Ni than for NbC. This reflects the much weaker C-metal interaction in Ni-C bonds compared with Nb-C. The comparison with the DOS also helps to identify the precise position of the Fermi level. We place the Fermi level at 282.9 eV.

## CONCLUSIONS

In summary, our interpretation of the spectroscopic results are consistent with our previous interpretations of the AES and XPS data [6], and with Darling's EMT theoretical results as discussed above [1]. First, the CEELS data do indeed verify that significant horizontal C-C bonding exists on the surface below 600K. We anticipate that this is in the form of  $C_n$ . Around 620K, some vertical  $C_2$  is formed along with considerable  $C_1$  (i.e. atomic C). However, the CEELS and NEXAFS data also suggest that vertical  $C_2$  is formed only at higher coverages (it is clearly present in the Caputi data [coverage about 1 ML] but absent in Stohr and Jaeger's NEXAFS data [coverage < 0.5 ML]). At higher coverages, we envisage that some of the  $C_2$  are forced to flip up to make room for the neighboring horizontal  $C_2$ 's to dissociate. These vertical  $C_2$ 's may then serve as the precursor for the nucleation of graphite, since it would explain the lack of graphite formation from  $C_2H_4$ /Ni(100) (i.e. at low carbon coverages). Further exposure to  $C_2H_2$  at higher temperatures (i.e. producing higher C coverages) does lead to graphite formation on Ni(100) [9]. Thus we provide the first experimental evidence for vertical  $C_2$  as a precursor for graphite nucleation and corroborate the theoretical EMT [1] results.

\*Support from the Office of Naval Research is gratefully acknowledged.

## REFERENCES

1. G.R. Darling, J.B. Pendry, and R.W. Joyner, *Surf. Sci.* **221**, 69 (1989).
2. J.A. Horsley, J. Stohr, and R.J. Koestner, *J. Chem. Phys.* **83**, 3146 (1985).
3. L.S. Caputi, G. Chiarello, and L. Papagno, *Surf. Sci.* **162**, 259 (1985).
4. R. Rosei, S. Modesti, F. Sette, C. Quaresima, A. Savoia, and P. Perfetti, *Phys. Rev.* **B29**, 3416 (1984).
5. J. Stohr and R. Jaeger, *Phys. Rev.* **B26**, 4111 (1982).
6. F.L. Hutson, D.E. Ramaker, and B.E. Koel, submitted to *Surf. Sci.*
7. T.T.P. Cheung, *Phys. Rev.* **B31**, 4792 (1985).
8. D.A. Outka and J. Stohr, in Chemistry and Physics of Solid Surfaces VII, edited by R. Vanselow and R. Howe (Springer-Verlag, Heidelberg, 1988), p.20.
9. S.C. Gebhard and B.E. Koel (unpublished).
10. D.E. Ramaker and F.L. Hutson, submitted to *Phys. Rev. B*.
11. D. Wesner, S. Krummacher, M. Strongin, R. Carr, T.K. Sham, W. Eberhardt and S.L. Weng, *Phys. Rev.* **B30**, 855, 1984.
12. K. Schwarz, *J. Phys. C: Solid State Phys.* **10**, 195 (1977); **8**, 809 (1975).
13. P.J. Feibelman, *Phys. Rev.* **B26**, 5347 (1982).



TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)  
Chemistry Division, Code 1113  
800 North Quincy Street  
Arlington, Virginia 22217-5000

Commanding Officer (1)  
Naval Weapons Support Center  
Dr. Bernard E. Douda  
Crane, Indiana 47522-5050

Dr. Richard W. Drisko (1)  
Naval Civil Engineering  
Laboratory  
Code L52  
Port Hueneme, CA 93043

David Taylor Research Center (1)  
Dr. Eugene C. Fischer  
Annapolis, MD 21402-5067

Dr. James S. Murday (1)  
Chemistry Division, Code 6100  
Naval Research Laboratory  
Washington, D.C. 20375-5000

Defense Technical Information Center  
Building 5, Cameron Station  
Alexandria, VA 22314

Dr. Robert Green, Director (1)  
Chemistry Division, Code 385  
Naval Weapons Center  
China Lake, CA 93555-6001

Chief of Naval Research (1)  
Special Assistant for Marine  
Corps Matters  
Code 00MC  
800 North Quincy Street  
Arlington, VA 22217-5000

Dr. Bernadette Eichinger (1)  
Naval Ship Systems Engineering  
Station  
Code 053  
Philadelphia Naval Base  
Philadelphia, PA 19112

Dr. Sachio Yamamoto (1)  
Naval Ocean Systems Center  
Code 52  
San Diego, CA 92152-5000

Dr. Harold H. Singerman (1)  
David Taylor Research Center  
Code 283  
Annapolis, MD 21402-5067

ENCLOSURE(-)

FY90 Abstracts Distribution List for Solid State & Surface Chemistry

Professor John Baldeschwieler  
Department of Chemistry  
California Inst. of Technology  
Pasadena, CA 91125

Professor Paul Barbara  
Department of Chemistry  
University of Minnesota  
Minneapolis, MN 55455-0431

Dr. Duncan Brown  
Advanced Technology Materials  
520-B Danury Rd.  
New Milford, CT 06776

Professor Stanley Bruckenstein  
Department of Chemistry  
State University of New York  
Buffalo, NY 14214

Professor Carolyn Cassady  
Department of Chemistry  
Miami University  
Oxford, OH 45056

Professor R.P.H. Chang  
Dept. Matls. Sci. & Engineering  
Northwestern University  
Evanston, IL 60208

Professor Frank DiSalvo  
Department of Chemistry  
Cornell University  
Ithaca, NY 14853

Dr. James Duncan  
Federal Systems Division  
Eastman Kodak Company  
Rochester, NY 14650-2156

Professor Arthur Ellis  
Department of Chemistry  
University of Wisconsin  
Madison, WI 53706

Professor Mustafa El-Sayed  
Department of Chemistry  
University of California  
Los Angeles, CA 90024

Professor John Eyler  
Department of Chemistry  
University of Florida  
Gainesville, FL 32611

Professor James Garvey  
Department of Chemistry  
State University of New York  
Buffalo, NY 14214

Professor Steven George  
Department of Chemistry  
Stanford University  
Stanford, CA 94305

Professor Tom George  
Dept. of Chemistry & Physics  
State University of New York  
Buffalo, NY 14260

Dr. Robert Hamers  
IBM T.J. Watson Research Center  
P.O. Box 218  
Yorktown Heights, NY 10598

Professor Paul Hansma  
Department of Physics  
University of California  
Santa Barbara, CA 93106

Professor Charles Harris  
Department of Chemistry  
University of California  
Berkeley, CA 94720

Professor John Hemminger  
Department of Chemistry  
University of California  
Irvine, CA 92717

Professor Roald Hoffmann  
Department of Chemistry  
Cornell University  
Ithaca, NY 14853

Professor Leonard Interrante  
Department of Chemistry  
Rensselaer Polytechnic Institute  
Troy, NY 12181

Professor Eugene Irene  
Department of Chemistry  
University of North Carolina  
Chapel Hill, NC 27514

Dr. Sylvia Johnson  
SRI International  
333 Ravenswood Avenue  
Menlo Park, CA 94025

Dr. Zakya Kafafi  
Code 6551  
Naval Research Laboratory  
Washington, DC 20375-5000

Professor Larry Kesmodel  
Department of Physics  
Indiana University  
Bloomington, IN 47403

Professor Max Lagally  
Dept. Metal. & Min. Engineering  
University of Wisconsin  
Madison, WI 53706

Dr. Stephen Lieberman  
Code 522  
Naval Ocean Systems Center  
San Diego, CA 92152

Professor M.C. Lin  
Department of Chemistry  
Emory University  
Atlanta, GA 30322

Professor Fred McLafferty  
Department of Chemistry  
Cornell University  
Ithaca, NY 14853-1301

Professor Horia Metiu  
Department of Chemistry  
University of California  
Santa Barbara, CA 93106

Professor Larry Miller  
Department of Chemistry  
University of Minnesota  
Minneapolis, MN 55455-0431

Professor George Morrison  
Department of Chemistry  
Cornell University  
Ithaca, NY 14853

Professor Daniel Neumark  
Department of Chemistry  
University of California  
Berkeley, CA 94720

Professor David Ramaker  
Department of Chemistry  
George Washington University  
Washington, DC 20052

Dr. Gary Rubloff  
IBM T.J. Watson Research Center  
P.O. Box 218  
Yorktown Heights, NY 10598

Professor Richard Smalley  
Department of Chemistry  
Rice University  
P.O. Box 1892  
Houston, TX 77251

Professor Gerald Stringfellow  
Dept. of Matls. Sci. & Engineering  
University of Utah  
Salt Lake City, UT 84112

Professor Galen Stucky  
Department of Chemistry  
University of California  
Santa Barbara, CA 93106

Professor H. Tachikawa  
Department of Chemistry  
Jackson State University  
Jackson, MI 39217-0510

Professor William Unertl  
Lab. for Surface Sci. & Technology  
University of Maine  
Orono, ME 04469

Dr. Terrell Vanderah  
Code 3854  
Naval Weapons Center  
China Lake, CA 93555

Professor John Weaver  
Dept. of Chem. & Mat. Sciences  
University of Minnesota  
Minneapolis, MN 55455

Professor Brad Weiner  
Department of Chemistry  
University of Puerto Rico  
Rio Piedras, Puerto Rico 00931

Professor Robert Whetten  
Department of Chemistry  
University of California  
Los Angeles, CA 90024

Professor R. Stanley Williams  
Department of Chemistry  
University of California  
Los Angeles, CA 90024

Professor Nicholas Winograd  
Department of Chemistry  
Pennsylvania State University  
University Park, PA 16802

Professor Aaron Wold  
Department of Chemistry  
Brown University  
Providence, RI 02912

Professor Vicki Wysocki  
Department of Chemistry  
Virginia Commonwealth University  
Richmond, VA 23284-2006

Professor John Yates  
Department of Chemistry  
University of Pittsburgh  
Pittsburgh, PA 15260